

Hilti HIT-RE 500-SD mortar with HIS-(R)N sleeve

Injection mortar system	Benefits
 <p>Hilti HIT-RE 500-SD 330 ml foil pack (also available as 500 ml and 1400 ml foil pack)</p> <p>Statik mixer</p> <p>HIS-(R)N sleeve</p>	<ul style="list-style-type: none"> - SAFEset technology: drilling and borehole cleaning in one step with Hilti hollow drill bit - suitable for cracked and non-cracked concrete C 20/25 to C 50/60 - ETA seismic approval C1 - high loading capacity - suitable for dry and water saturated concrete - long working time at elevated temperatures - odourless epoxy



Concrete




Tensile zone



Seismic
ETA-C1



Shock




Small edge distance and spacing



Fire resistance

SAFEset

Hilti SAFEset technology with hollow drill bit



Corrosion resistance



European Technical Approval



CE conformity



PROFIS Anchor design software

Approvals / certificates

Description	Authority / Laboratory	No. / date of issue
European technical approval ^{a)}	DIBt, Berlin	ETA-07/0260 / 2013-06-26
ES report incl. seismic	ICC evaluation service	ESR 2322 / 2014-02-01
Shockproof fastenings in civil defence installations	Federal Office for Civil Protection, Bern	BZS D 08-604 / 2009-10-21
Fire test report	MFPA, Leipzig	GS-III/B-07-070 / 2008-01-18
Assessment report (fire)	warringtonfire	WF 327804/B / 2013-07-10

a) All data given in this section according ETA-07/0260, issue 2013-06-26.

Basic loading data (for a single anchor)

All data in this section applies to

For details see Simplified design method

- Correct setting (See setting instruction)
- No edge distance and spacing influence
- Steel failure
- Screw strength class 8.8
- Base material thickness, as specified in the table
- One typical embedment depth, as specified in the table
- One anchor material, as specified in the tables
- Concrete C 20/25, $f_{ck,cube} = 25 \text{ N/mm}^2$
- Temperature range I
(min. base material temperature -40°C , max. long term/short term base material temperature: $+24^\circ\text{C}/40^\circ\text{C}$)
- Installation temperature range $+5^\circ\text{C}$ to $+40^\circ\text{C}$

Embedment depth and base material thickness for the basic loading data.

Mean ultimate resistance, characteristic resistance, design resistance, recommended loads.

Anchor size	M8	M10	M12	M16	M20
Embedment depth [mm]	90	110	125	170	205
Base material thickness [mm]	120	150	170	230	270

Mean ultimate resistance: concrete C 20/25 – $f_{ck,cube} = 25 \text{ N/mm}^2$, anchor HIS-N

Data according ETA-07/0260, issue 2013-06-26							
Anchor size			M8	M10	M12	M16	M20
Non cracked concrete							
Tensile $N_{Ru,m}$	HIS-N	[kN]	26,3	48,3	70,4	123,9	114,5
Shear $V_{Ru,m}$	HIS-N	[kN]	13,7	24,2	41,0	62,0	57,8
Cracked concrete							
Tensile $N_{Ru,m}$	HIS-N	[kN]	26,3	48,3	67,1	106,4	114,5
Shear $V_{Ru,m}$	HIS-N	[kN]	13,7	24,2	41,0	62,0	57,8

Characteristic resistance: concrete C 20/25 – $f_{ck,cube} = 25 \text{ N/mm}^2$, anchor HIS-N

Data according ETA-07/0260, issue 2013-06-26							
Anchor size			M8	M10	M12	M16	M20
Non cracked concrete							
Tensile N_{Rk}	HIS-N	[kN]	25,0	46,0	67,0	111,9	109,0
Shear V_{Rk}	HIS-N	[kN]	13,0	23,0	39,0	59,0	55,0
Cracked concrete							
Tensile N_{Rk}	HIS-N	[kN]	25,0	40,0	50,3	79,8	105,7
Shear V_{Rk}	HIS-N	[kN]	13,0	23,0	39,0	59,0	55,0

Design resistance: concrete C 20/25 – $f_{ck,cube} = 25 \text{ N/mm}^2$, anchor HIS-N

Data according ETA-07/0260, issue 2013-06-26							
Anchor size			M8	M10	M12	M16	M20
Non cracked concrete							
Tensile N_{Rd}	HIS-N	[kN]	16,8	27,7	33,6	53,3	70,6
Shear V_{Rd}	HIS-N	[kN]	10,4	18,4	26,0	39,3	36,7
Cracked concrete							
Tensile N_{Rd}	HIS-N	[kN]	13,9	19,0	24,0	38,0	50,3
Shear V_{Rd}	HIS-N	[kN]	10,4	18,4	26,0	39,3	36,7

Recommended loads ^{a)}: concrete C 20/25 – $f_{ck,cube} = 25 \text{ N/mm}^2$, anchor HIS-N

			Data according ETA-07/0260, issue 2013-06-26				
Anchor size			M8	M10	M12	M16	M20
Non cracked concrete							
Tensile N_{rec}	HIS-N	[kN]	12,0	19,8	24,0	38,1	50,4
Shear V_{rec}	HIS-N	[kN]	7,4	13,1	18,6	28,1	26,2
Cracked concrete							
Tensile N_{rec}	HIS-N	[kN]	9,9	13,6	17,1	27,1	35,9
Shear V_{rec}	HIS-N	[kN]	7,4	13,1	18,6	28,1	26,2

a) With overall partial safety factor for action $\gamma = 1,4$. The partial safety factors for action depend on the type of loading and shall be taken from national regulations.

Service temperature range

Hilti HIT-RE 500-SD injection mortar may be applied in the temperature ranges given below. An elevated base material temperature may lead to a reduction of the design bond resistance.

Temperature range	Base material temperature	Maximum long term base material temperature	Maximum short term base material temperature
Temperature range I	-40 °C to +40 °C	+24 °C	+40 °C
Temperature range II	-40 °C to +58 °C	+35 °C	+58 °C
Temperature range III	-40 °C to +70 °C	+43 °C	+70 °C

Max short term base material temperature

Short-term elevated base material temperatures are those that occur over brief intervals, e.g. as a result of diurnal cycling.

Max long term base material temperature

Long-term elevated base material temperatures are roughly constant over significant periods of time.

Materials

Mechanical properties of HIS-(R)N

			Data according ETA-07/0260, issue 2013-06-26				
Anchor size			M8	M10	M12	M16	M20
Nominal tensile strength f_{uk}	HIS-N	[N/mm ²]	490	490	460	460	460
	Screw 8.8	[N/mm ²]	800	800	800	800	800
	HIS-RN	[N/mm ²]	700	700	700	700	700
	Screw A4-70	[N/mm ²]	700	700	700	700	700
Yield strength f_{yk}	HIS-N	[N/mm ²]	410	410	375	375	375
	Screw 8.8	[N/mm ²]	640	640	640	640	640
	HIS-RN	[N/mm ²]	350	350	350	350	350
	Screw A4-70	[N/mm ²]	450	450	450	450	450
Stressed cross-section A_s	HIS-(R)N	[mm ²]	51,5	108,0	169,1	256,1	237,6
	Screw	[mm ²]	36,6	58	84,3	157	245
Moment of resistance W	HIS-(R)N	[mm ³]	145	430	840	1595	1543
	Screw	[mm ³]	31,2	62,3	109	277	541

Material quality

Part	Material
internally threaded sleeves ^{a)} HIS-N	C-steel 1.0718, steel galvanized $\geq 5\mu\text{m}$
internally threaded sleeves ^{b)} HIS-RN	stainless steel 1.4401 and 1.4571

a) related fastening screw: strength class 8.8, A5 > 8% Ductile
steel galvanized $\geq 5\mu\text{m}$

b) related fastening screw: strength class 70, A5 > 8% Ductile
stainless steel 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362

Anchor dimensions

Anchor size	M8	M10	M12	M16	M20
Internal sleeve HIS-(R)N	M8x90	M10x110	M12x125	M16x170	M20x205
Anchor embedment depth [mm]	90	110	125	170	205

Setting

installation equipment

Anchor size	M8	M10	M12	M16	M20
Rotary hammer	TE 2 – TE 16		TE 40 – TE 70		
Other tools	compressed air gun or blow out pump, set of cleaning brushes, dispenser				

Setting instruction

Bore hole drilling

	<p>Drill hole to the required embedment depth with an appropriately sized Hilti TE-CD or TE-YD hollow drill bit with Hilti vacuum attachment. This drilling system removes the dust and cleans the borehole during drilling when using in accordance with the user's manual.</p> <p>After drilling is complete, proceed to the "injection preparation" step in the instructions for use.</p>
	<p>Drill Hole to the required embedment depth with a hammer drill set in rotation-hammer mode using an appropriately sized carbide drill bit.</p>







Bore hole cleaning Just before setting an anchor, the bore hole must be free of dust and debris.

Compressed air cleaning (CAC) for all bore hole diameters d_0 and all bore hole depth h_0

	<p>Blow 2 times from the back of the hole (if needed with nozzle extension) over the hole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust.</p> <p>Bore hole diameter ≥ 32 mm the compressor must supply a minimum air flow of 140 m³/hour.</p>
	<p>Brush 2 times with the specified brush size by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it.</p> <p>The brush must produce natural resistance as it enters the bore hole -- if not the brush is too small and must be replaced with the proper brush diameter.</p>
	<p>Blow again with compressed air 2 times until return air stream is free of noticeable dust.</p>

Injection preparation

	<p>Tightly attach new Hilti mixing nozzle HIT-RE-M to foil pack manifold (snug fit). Do not modify the mixing nozzle.</p> <p>Observe the instruction for use of the dispenser and the mortar. Check foil pack holder for proper function. Do not use damaged foil packs / holders. Insert foil pack into foil pack holder and put holder into HIT-dispenser.</p>
	<p>The foil pack opens automatically as dispensing is initiated. Discard initial adhesive. Depending on the size of the foil pack an initial amount of adhesive has to be discarded.</p> <p>Discard quantities are:</p> <ul style="list-style-type: none"> 3 strokes for 330 ml foil pack, 4 strokes for 500 ml foil pack, 65 ml for 1400 ml foil pack $\leq 5^\circ\text{C}$.

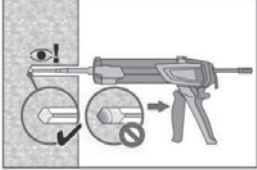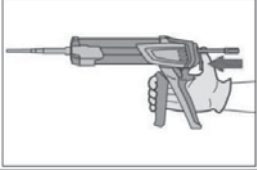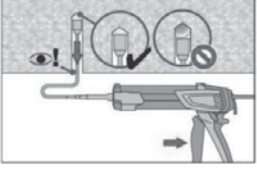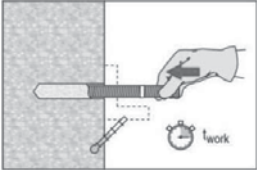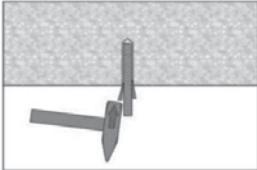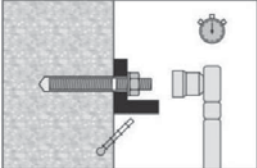Inject adhesive from the back of the borehole without forming air voids		
	Inject the adhesive starting at the back of the hole, slowly withdrawing the mixer with each trigger pull. Fill holes approximately 2/3 full. It is required that the annular gap between the anchor and the concrete is completely filled with adhesive along the embedment length.	
	After injection is completed, depressurize the dispenser by pressing the release trigger. This will prevent further adhesive discharge from the mixer.	
	Overhead installation and/or installation with embedment depth $h_{ef} > 250\text{mm}$. For overhead installation the injection is only possible with the aid of extensions and piston plugs. Assemble HIT-RE-M mixer, extension(s) and appropriately sized piston plug (HIT-SZ). Insert piston plug to back of the hole and inject adhesive. During injection the piston plug will be naturally extruded out of the bore hole by the adhesive pressure.	
Setting the element		
	Before use, verify that the element is dry and free of oil and other contaminants. Mark and set element to the required embedment depth until working time t_{work} has elapsed.	
	For overhead installation use piston plugs and fix embedded parts with e.g. wedges HIT-OHW.	
	Loading the anchor: After required curing time t_{cure} the anchor can be loaded. The applied installation torque shall not exceed given T_{max} .	

For detailed information on installation see instruction for use given with the package of the product.

Curing time for general conditions

Data according ETA-07/0260, issue 2013-06-26		
Temperature of the base material	Working time in which anchor can be inserted and adjusted t_{gel}	Curing time before anchor can be fully loaded t_{cure}
40 °C	12 min	4 h
30 °C to 39 °C	12 min	8 h
20 °C to 29 °C	20 min	12 h
15 °C to 19 °C	30 min	24 h
10 °C to 14 °C	90 min	48 h
5 °C to 9 °C	120 min	72 h

Setting details

		Data according ETA-07/0260, issue 2013-06-26				
Anchor size		M8	M10	M12	M16	M20
Nominal diameter of drill bit	d_0 [mm]	14	18	22	28	32
Diameter of element	d [mm]	12,5	16,5	20,5	25,4	27,6
Effective anchorage and drill hole depth	h_{ef} [mm]	90	110	125	170	205
Minimum base material thickness	h_{min} [mm]	120	150	170	230	270
Diameter of clearance hole in the fixture	d_f [mm]	9	12	14	18	22
Thread engagement length; min - max	h_s [mm]	8-20	10-25	12-30	16-40	20-50
Minimum spacing	s_{min} [mm]	40	45	55	65	90
Minimum edge distance	c_{min} [mm]	40	45	55	65	90
Critical spacing for splitting failure	$s_{cr,sp}$	$2 c_{cr,sp}$				
Critical edge distance for splitting failure ^{a)}	$c_{cr,sp}$ [mm]	$1,0 \cdot h_{ef}$ for $h / h_{ef} \geq 2,0$				
		$4,6 h_{ef} - 1,8 h$ for $2,0 > h / h_{ef} > 1,3$				
		$2,26 h_{ef}$ for $h / h_{ef} \leq 1,3$				
Critical spacing for concrete cone failure	$s_{cr,N}$	$2 c_{cr,N}$				
Critical edge distance for concrete cone failure ^{b)}	$c_{cr,N}$	$1,5 h_{ef}$				
Torque moment ^{c)}	T_{max} [Nm]	10	20	40	80	150

For spacing (edge distance) smaller than critical spacing (critical edge distance) the design loads have to be reduced.

- a) h : base material thickness ($h \geq h_{min}$)
- b) The critical edge distance for concrete cone failure depends on the embedment depth h_{ef} and the design bond resistance. The simplified formula given in this table is on the save side.
- c) This is the maximum recommended torque moment to avoid splitting failure during installation for anchors with minimum spacing and/or edge distance.

Simplified design method

Simplified version of the design method according ETAG 001, TR 029. Design resistance according data given in ETA-07/0260, issue 2013-06-26.

- Influence of concrete strength
- Influence of edge distance
- Influence of spacing
- Valid for a group of two anchors. (The method may also be applied for anchor groups with more than two anchors or more than one edge distance. The influencing factors must then be considered for each edge distance and spacing. The calculated design loads are then on the save side: They will be lower than the exact values according ETAG 001, TR 029. To avoid this, it is recommended to use the anchor design software PROFIS anchor)

The design method is based on the following simplification:

- No different loads are acting on individual anchors (no eccentricity)

The values are valid for one anchor.

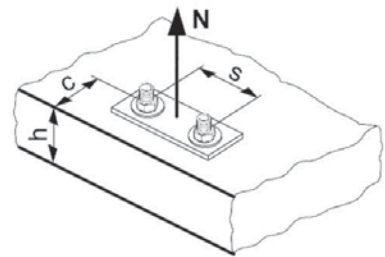
For more complex fastening applications please use the anchor design software PROFIS Anchor.

Tension loading

The design tensile resistance is the lower value of

- Steel resistance: $N_{Rd,s}$
- Combined pull-out and concrete cone resistance: $N_{Rd,p} = N_{Rd,p}^0 \cdot f_{B,p} \cdot f_{1,N} \cdot f_{2,N} \cdot f_{3,N} \cdot f_{h,p} \cdot f_{re,N}$
- Concrete cone resistance: $N_{Rd,c} = N_{Rd,c}^0 \cdot f_B \cdot f_{1,N} \cdot f_{2,N} \cdot f_{3,N} \cdot f_{h,N} \cdot f_{re,N}$
- Concrete splitting resistance (only non-cracked concrete): $N_{Rd,sp} = N_{Rd,c}^0 \cdot f_B \cdot f_{1,sp} \cdot f_{2,sp} \cdot f_{3,sp} \cdot f_{h,N}$

$f_{re,N}$



Basic design tensile resistance

Design steel resistance $N_{Rd,s}$

			Data according ETA-07/0260, issue 2013-06-26				
Anchor size			M8	M10	M12	M16	M20
$N_{Rd,s}$	HIS-N	[kN]	17,4	30,7	44,7	80,3	74,1
	HIS-RN	[kN]	13,9	21,9	31,6	58,8	69,2

Design combined pull-out and concrete cone resistance

$$N_{Rd,p} = N_{Rd,p}^0 \cdot f_{B,p} \cdot f_{1,N} \cdot f_{2,N} \cdot f_{3,N} \cdot f_{h,p} \cdot f_{re,N}$$

	Data according ETA-07/0260, issue 2013-06-26				
Anchor size	M8	M10	M12	M16	M20
Embedment depth h_{ef} [mm]	90	110	125	170	205
Non cracked concrete					
$N_{Rd,p}^0$ Temperature range I [kN]	22,2	28,6	45,2	81,0	95,2
$N_{Rd,p}^0$ Temperature range II [kN]	19,4	23,8	35,7	66,7	81,0
$N_{Rd,p}^0$ Temperature range III [kN]	11,1	14,3	19,0	35,7	45,2
Cracked concrete					
$N_{Rd,p}^0$ Temperature range I [kN]	13,9	19,0	28,6	45,2	54,8
$N_{Rd,p}^0$ Temperature range II [kN]	11,1	16,7	19,0	35,7	45,2
$N_{Rd,p}^0$ Temperature range III [kN]	6,7	9,5	11,9	19,0	23,8

$$\text{Design concrete cone resistance } N_{Rd,c} = N_{Rd,c}^0 \cdot f_B \cdot f_{1,N} \cdot f_{2,N} \cdot f_{3,N} \cdot f_{h,N} \cdot f_{re,N}$$

$$\text{Design splitting resistance } N_{Rd,sp} = N_{Rd,c}^0 \cdot f_B \cdot f_{1,sp} \cdot f_{2,sp} \cdot f_{3,sp} \cdot f_{h,N} \cdot f_{re,N}$$

	Data according ETA-07/0260, issue 2013-06-26				
Anchor size	M8	M10	M12	M16	M20
$N_{Rd,c}^0$ Non cracked concrete [kN]	24,0	27,7	33,6	53,3	70,6
$N_{Rd,c}^0$ Cracked concrete [kN]	17,1	19,8	24,0	38,0	50,3

a) Splitting resistance must only be considered for non-cracked concrete

Influencing factors

Influence of concrete strength on combined pull-out and concrete cone resistance

Concrete strength designation (ENV 206)	C 20/25	C 25/30	C 30/37	C 35/45	C 40/50	C 45/55	C 50/60
$f_{B,p} = (f_{ck,cube}/25N/mm^2)^{0,1}$ a)	1	1,02	1,04	1,06	1,07	1,08	1,09

a) $f_{ck,cube}$ = concrete compressive strength, measured on cubes with 150 mm side length

Influence of embedment depth on combined pull-out and concrete cone resistance

$$f_{h,p} = 1$$

Influence of concrete strength on concrete cone resistance

Concrete strength designation (ENV 206)	C 20/25	C 25/30	C 30/37	C 35/45	C 40/50	C 45/55	C 50/60
$f_B = (f_{ck,cube}/25N/mm^2)^{1/2}$ a)	1	1,1	1,22	1,34	1,41	1,48	1,55

a) $f_{ck,cube}$ = concrete compressive strength, measured on cubes with 150 mm side length

Influence of edge distance ^{a)}

$c/c_{cr,N}$	0,1	0,2	0,3	0,4	0,5	0,6	0,7	0,8	0,9	1
$c/c_{cr,sp}$										
$f_{1,N} = 0,7 + 0,3 \cdot c/c_{cr,N}$	0,73	0,76	0,79	0,82	0,85	0,88	0,91	0,94	0,97	1
$f_{1,sp} = 0,7 + 0,3 \cdot c/c_{cr,sp}$										
$f_{2,N} = 0,5 \cdot (1 + c/c_{cr,N})$	0,55	0,60	0,65	0,70	0,75	0,80	0,85	0,90	0,95	1
$f_{2,sp} = 0,5 \cdot (1 + c/c_{cr,sp})$										

a) The edge distance shall not be smaller than the minimum edge distance c_{min} given in the table with the setting details. These influencing factors must be considered for every edge distance smaller than the critical edge distance.

Influence of anchor spacing ^{a)}

$s/s_{cr,N}$	0,1	0,2	0,3	0,4	0,5	0,6	0,7	0,8	0,9	1
$s/s_{cr,sp}$										
$f_{3,N} = 0,5 \cdot (1 + s/s_{cr,N})$	0,55	0,60	0,65	0,70	0,75	0,80	0,85	0,90	0,95	1
$f_{3,sp} = 0,5 \cdot (1 + s/s_{cr,sp})$										

a) The anchor spacing shall not be smaller than the minimum anchor spacing s_{min} given in the table with the setting details. This influencing factor must be considered for every anchor spacing.

Influence of embedment depth on concrete cone resistance

$f_{h,N} = 1$

Influence of reinforcement


h_{ef} [mm]	80	90	≥ 100
$f_{re,N} = 0,5 + h_{ef}/200mm \leq 1$	0,9 ^{a)}	0,95 ^{a)}	1

a) This factor applies only for dense reinforcement. If in the area of anchorage there is reinforcement with a spacing ≥ 150 mm (any diameter) or with a diameter ≤ 10 mm and a spacing ≥ 100 mm, then a factor $f_{re} = 1$ may be applied.

Shear loading

The design shear resistance is the lower value of

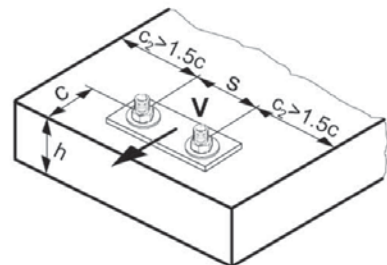- Steel resistance: $V_{Rd,s}$
- Concrete pryout resistance: $V_{Rd,cp} = k \cdot \text{lower value of } N_{Rd,p} \text{ and } N_{Rd,c}$
- Concrete edge resistance: $V_{Rd,c} = V_{Rd,c}^0 \cdot f_B \cdot f_{B'} \cdot f_h \cdot f_4 \cdot f_{hef} \cdot f_c$



Basic design shear resistance

Design steel resistance $V_{Rd,s}$

		Data according ETA-07/0260, issue 2013-06-26				
Anchor size		M8	M10	M12	M16	M20
$V_{Rd,s}$	HIS-N [kN]	10,4	18,4	26,0	39,3	36,7
	HIS-RN [kN]	8,3	12,8	19,2	35,3	41,5

Design concrete pryout resistance $V_{Rd,cp}$ = lower value^{a)} of $k \cdot N_{Rd,p}$ and $k \cdot N_{Rd,c}$

$$k = 1 \text{ for } h_{ef} < 60 \text{ mm}$$

$$k = 2 \text{ for } h_{ef} \geq 60 \text{ mm}$$

- a) $N_{Rd,p}$: Design combined pull-out and concrete cone resistance
 $N_{Rd,c}$: Design concrete cone resistance

Design concrete edge resistance $V_{Rd,c} = V_{Rd,c}^0 \cdot f_B \cdot f_{\beta} \cdot f_h \cdot f_4 \cdot f_{hef} \cdot f_c$

Anchor size	M8	M10	M12	M16	M20
Non-cracked concrete					
$V_{Rd,c}^0$ [kN]	12,4	19,6	28,2	40,2	46,2
Cracked concrete					
$V_{Rd,c}^0$ [kN]	8,8	13,9	20,0	28,5	32,7

Influencing factors

Influence of concrete strength

Concrete strength designation (ENV 206)	C 20/25	C 25/30	C 30/37	C 35/45	C 40/50	C 45/55	C 50/60
$f_B = (f_{ck,cube}/25\text{N/mm}^2)^{1/2}$ a)	1	1,1	1,22	1,34	1,41	1,48	1,55

- a) $f_{ck,cube}$ = concrete compressive strength, measured on cubes with 150 mm side length

Influence of angle between load applied and the direction perpendicular to the free edge

Angle β	0°	10°	20°	30°	40°	50°	60°	70°	80°	≥ 90°
$f_{\beta} = \frac{1}{\sqrt{(\cos \alpha_r)^2 + \left(\frac{\sin \alpha_r}{2,5}\right)^2}}$	1	1,01	1,05	1,13	1,24	1,40	1,64	1,97	2,32	2,50

Influence of base material thickness

h/c	0,15	0,3	0,45	0,6	0,75	0,9	1,05	1,2	1,35	≥ 1,5
$f_h = \{h/(1,5 \cdot c)\}^{1/2} \leq 1$	0,32	0,45	0,55	0,63	0,71	0,77	0,84	0,89	0,95	1,00

Influence of anchor spacing and edge distance ^{a)} for concrete edge resistance: f_4
 $f_4 = (c/h_{ef})^{1,5} \cdot (1 + s / [3 \cdot c]) \cdot 0,5$

c/h _{ef}	Single anchor	Group of two anchors s/h _{ef}														
		0,75	1,50	2,25	3,00	3,75	4,50	5,25	6,00	6,75	7,50	8,25	9,00	9,75	10,50	11,25
0,50	0,35	0,27	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35	0,35
0,75	0,65	0,43	0,54	0,65	0,65	0,65	0,65	0,65	0,65	0,65	0,65	0,65	0,65	0,65	0,65	0,65
1,00	1,00	0,63	0,75	0,88	1,00	1,00	1,00	1,00	1,00	1,00	1,00	1,00	1,00	1,00	1,00	1,00
1,25	1,40	0,84	0,98	1,12	1,26	1,40	1,40	1,40	1,40	1,40	1,40	1,40	1,40	1,40	1,40	1,40
1,50	1,84	1,07	1,22	1,38	1,53	1,68	1,84	1,84	1,84	1,84	1,84	1,84	1,84	1,84	1,84	1,84
1,75	2,32	1,32	1,49	1,65	1,82	1,98	2,15	2,32	2,32	2,32	2,32	2,32	2,32	2,32	2,32	2,32
2,00	2,83	1,59	1,77	1,94	2,12	2,30	2,47	2,65	2,83	2,83	2,83	2,83	2,83	2,83	2,83	2,83
2,25	3,38	1,88	2,06	2,25	2,44	2,63	2,81	3,00	3,19	3,38	3,38	3,38	3,38	3,38	3,38	3,38
2,50	3,95	2,17	2,37	2,57	2,77	2,96	3,16	3,36	3,56	3,76	3,95	3,95	3,95	3,95	3,95	3,95
2,75	4,56	2,49	2,69	2,90	3,11	3,32	3,52	3,73	3,94	4,15	4,35	4,56	4,56	4,56	4,56	4,56
3,00	5,20	2,81	3,03	3,25	3,46	3,68	3,90	4,11	4,33	4,55	4,76	4,98	5,20	5,20	5,20	5,20
3,25	5,86	3,15	3,38	3,61	3,83	4,06	4,28	4,51	4,73	4,96	5,18	5,41	5,63	5,86	5,86	5,86
3,50	6,55	3,51	3,74	3,98	4,21	4,44	4,68	4,91	5,14	5,38	5,61	5,85	6,08	6,31	6,55	6,55
3,75	7,26	3,87	4,12	4,36	4,60	4,84	5,08	5,33	5,57	5,81	6,05	6,29	6,54	6,78	7,02	7,26
4,00	8,00	4,25	4,50	4,75	5,00	5,25	5,50	5,75	6,00	6,25	6,50	6,75	7,00	7,25	7,50	7,75
4,25	8,76	4,64	4,90	5,15	5,41	5,67	5,93	6,18	6,44	6,70	6,96	7,22	7,47	7,73	7,99	8,25
4,50	9,55	5,04	5,30	5,57	5,83	6,10	6,36	6,63	6,89	7,16	7,42	7,69	7,95	8,22	8,49	8,75
4,75	10,35	5,45	5,72	5,99	6,27	6,54	6,81	7,08	7,36	7,63	7,90	8,17	8,45	8,72	8,99	9,26
5,00	11,18	5,87	6,15	6,43	6,71	6,99	7,27	7,55	7,83	8,11	8,39	8,66	8,94	9,22	9,50	9,78
5,25	12,03	6,30	6,59	6,87	7,16	7,45	7,73	8,02	8,31	8,59	8,88	9,17	9,45	9,74	10,02	10,31
5,50	12,90	6,74	7,04	7,33	7,62	7,92	8,21	8,50	8,79	9,09	9,38	9,67	9,97	10,26	10,55	10,85

a) The anchor spacing and the edge distance shall not be smaller than the minimum anchor spacing s_{min} and the minimum edge distance c_{min} .

Influence of embedment depth

Anchor size	M8	M10	M12	M16	M20
$f_{hef} =$	1,38	1,21	1,04	1,22	1,45

Influence of edge distance ^{a)}

c/d	4	6	8	10	15	20	30	40
$f_c = (d/c)^{0,19}$	0,77	0,71	0,67	0,65	0,60	0,57	0,52	0,50

a) The edge distance shall not be smaller than the minimum edge distance c_{min} .

Combined tension and shear loading

For combined tension and shear loading see section "Anchor Design".

Seismic design C1

Basic loading data for concrete C20/25 – C50/60

All data in this section applies to:

- Seismic design according to TR045

The following technical data are based on: ETA-07/0260, issue 2013-06-26

Anchorage depth range

Anchor size	M8	M10	M12	M16	M20
Effective anchorage depth h_{ef} [mm]	90	110	125	170	205

Tension resistance in case of seismic performance category C1

Anchor size	M8	M10	M12	M16	M20	
Diameter of element	12,5	16,5	20,5	25,4	27,6	
Characteristic tension resistance to steel failure						
HIS-N steel grade 8.8	$N_{Rk,s,seis}$ [kN]	25	46	67	118	109
Partial safety factor	$\gamma_{Ms,seis}$ [-]	1,43	1,5		1,47	
HIS-RN steel grade 70	$N_{Rk,s,seis}$ [kN]	26	41	59	110	166
Partial safety factor	$\gamma_{Ms,seis}$ [-]	1,87			2,4	
Characteristic bond resistance in cracked concrete C20/25 to C50/60						
Temperature range I: 40°C/24°C	$N_{Rk,p,seis}$ [N/mm ²]	20	30	42	61	71
Temperature range II: 58°C/35°C	$N_{Rk,p,seis}$ [N/mm ²]	16	26	28	48	59
Temperature range III: 70°C/43°C	$N_{Rk,p,seis}$ [N/mm ²]	9,5	15	17	25	31
Partial safety factor	$\gamma_{Mp,seis}$ [-]	1,8	2,1			
Concrete cone resistance and splitting resistance						
Partial safety factor	$\gamma_{Mc,seis} = \gamma_{Msp,seis}$ [-]	1,8	2,1			

Displacement under tension load in case of seismic performance category C1 ¹⁾

Anchor size	M8	M10	M12	M16	M20
Displacement ¹⁾ $\delta_{N,seis}$ [mm]	1,5	1,7	1,9	2,3	2,7

1) Maximum displacement during cycling (seismic event).

Shear resistance in case of seismic performance category C1

Anchor size	M8	M10	M12	M16	M20	
Characteristic shear resistance to steel failure						
HIS-N steel grade 8.8	$N_{Rk,s,seis}$ [kN]	9	16	27	41	39
Partial safety factor	$\gamma_{Ms,seis}$ [-]	1,25		1,5		
HIS-RN steel grade 70	$N_{Rk,s,seis}$ [kN]	9	14	21	39	58
Partial safety factor	$\gamma_{Ms,seis}$ [-]	1,56			2,0	
Concrete pryout resistance and concrete edge resistance						
Partial safety factor	$\gamma_{Mcp,seis} = \gamma_{Mc,seis}$ [-]	1,5				

Displacement under shear load in case of seismic performance category C1 ¹⁾

Anchor size	M8	M10	M12	M16	M20
Displacement ¹⁾ $\delta_{V,seis}$ [mm]	3,2	3,5	3,8	4,4	5,0

1) Maximum displacement during cycling (seismic event).

For seismic resistant fastening applications please use the anchor design software PROFIS Anchor.

